

Mr. J. H. ...
7/44 T.N. 942
RESTRICTED

NATIONAL ADVISORY COMMITTEE FOR AERONAUTICS

TECHNICAL NOTE

No. 942

THE SHEAR STRENGTH OF ALUMINUM ALLOY DRIVEN RIVETS
AS AFFECTED BY INCREASING D/t RATIOS

By E. C. Hartmann and C. Wescoat
Aluminum Company of America



Washington
July 1944

~~CLASSIFIED-DOCUMENT-~~

This document contains classified information affecting the National Defense of the United States within the meaning of the Espionage Act, USC 50:31 and 32. Its transmission or the revelation of its contents in any manner to an unauthorized person is prohibited by law. Information so classified

may be imparted only to persons in the military and naval Services of the United States, appropriate civilian officers and employees of the Federal Government who have a legitimate interest therein, and to United States citizens of known loyalty and discretion who of necessity must be informed thereof.

RESTRICTED

RESTRICTED

NATIONAL ADVISORY COMMITTEE FOR AERONAUTICS

TECHNICAL NOTE NO. 942

THE SHEAR STRENGTH OF ALUMINUM ALLOY DRIVEN RIVETS
AS AFFECTED BY INCREASING D/t RATIOS

By E. C. Hartmann and G. Wescoat

INTRODUCTION AND OBJECT

A decrease in shear strengths for increasing D/t ratios was shown in a previous investigation of protruding-head aluminum alloy rivets in double shear conducted at Aluminum Research Laboratories in 1942. Since single shear joints are more common than double shear joints, it was desirable to extend the investigation to single shear joints. This report describes the results of this investigation of single shear joints and also includes the results of the previous investigation on double shear joints.

MATERIAL AND SPECIMENS

For all specimens button-head aluminum alloy rivets 1/2 inch in diameter were used. To obtain a wide range of shear strengths rivet alloys 53S-O, 53S-T61, 53S-T, and 17S-T were used. The 17S-T rivets were driven immediately after quenching, and all others were driven in the tempers indicated. 24S-T alloy plate and sheet were employed in thicknesses of 1/2, 3/8, 1/4, 3/16, 1/8, 0.081, and 0.064 inch.

The test panels were made up as shown in the sketch in figure 1. These panels then were cut to provide three single butt-strap specimens each $2\frac{3}{8}$ inches wide containing one rivet on each side of the joint. Thicknesses of main and strap plates were the same except in one group where the thicknesses of the strap plates were varied; while the thickness of the main plates was held constant at 3/8 inch.

RESTRICTED

The rivets were driven in 33/64-inch drilled and reamed holes with cone-point heads except in one case where flat-driven heads were used.

PROCEDURE

One of the three specimens from each set of three for each rivet alloy except 53S-T was tested in tension in a 20,000-pound capacity Amsler testing machine (Serial No. 4725, Type 10SZBDA). Movement of the main plates relative to the strap plate in this specimen was measured as indicated in figure 2 by means of fine lines scribed across the edges of the plates opposite the center lines of the rivets. The movements were measured as the displacement of this line at the faying surfaces, the readings being taken at four locations with a hand Brinell microscope reading direct to 0.1 millimeter and by estimation to 0.02 millimeter. The remaining two specimens of each group of three were tested in tension in the 40,000-pound capacity Amsler testing machine (Serial No. 4318, Type 20ZBDA) without any readings for movements of the plate.

RESULTS AND DISCUSSION

The results of the tests are shown in detail in table I and are summarized in table II. Figure 3 shows the results of the tests plotted to show the decrease in shear strength resulting from an increase in the bearing stress on the rivets. Ratios of shear strength to basic shear strength are used as ordinates and ratios of bearing stress to basic shear strength as abscissas, thus providing a nondimensional plot of the test results. Basic shear strength as used here is the shear strength obtained when the ratio of rivet diameter D to plate thickness t is unity ($D/t = 1$).

A study of table II and figure 3 indicates that the ratio of shear strength to basic shear strength reduces at nearly the same rate regardless of rivet alloys. The single shear strength starts to drop off noticeably when the bearing strength exceeds about $2\frac{1}{2}$ times the basic shear strength. A dotted curve has been drawn in figure 3 to show the trend of the double shear tests data in table III taken from the previous report. It is evident

that the decrease of double shear strength starts at about the same value of bearing strength as the decrease in single shear strength but that the reduction is more rapid in the double shear than in the single shear tests.

The data in figure 3 have been replotted in figure 4 using diameter-to-thickness ratios as abscissas. In this figure a simple straight line has been drawn to indicate the trend of the data. Such a straight line appears to be a close enough approximation of the test results to be useful for establishing allowable design values in actual practice. Using such a straight-line formula, a simple rule could be written for allowable single shear strength of protruding-head aluminum alloy rivets driven in aluminum alloy plates as follows:

For values of D/t up to 3,

Single shear strength = basic allowable single shear strength

For values of D/t greater than 3,

Single shear strength = basic allowable single shear strength $\times [1 - 0.04 (D/t - 3)]$,

where

D nominal diameter of rivet, inch

t thickness of plate, inch

The fact that a straight-line formula seems to be acceptable in the case of single shear tests suggests that a similar straight-line formula might well be used in connection with double shear tests. Having this in mind, the double shear data in table III taken from the previous report have been replotted in figure 5; and, based on this replot, the following rule can be stated for determining the double shear strength of protruding head aluminum alloy rivets in aluminum alloy plates:

For values of D/t up to 1.5,

Double shear strength = basic allowable double shear strength

For values of D/t greater than 1.5,

$$\text{Double shear strength} = \text{basic allowable double shear strength} \times [1 - 0.13 (D/t - 1.5)].$$

In aircraft design the present method of taking account of the reduced shear strength of rivets resulting from increasing D/t ratios is to limit the allowable bearing stress on the rivets to $3\frac{1}{3}$ times the basic shear strength. (See reference 1.) Figure 6 shows a comparison of this present rule with the proposed new rules in double shear and single shear. The small area marked "A" in each figure indicates the range in which the proposed new rule is slightly more conservative (up to 8 percent) than the present rule, and the large area marked "B" in each figure indicates the range in which the proposed new rule gives higher allowable values than the present rule.

These differences are further brought out in table IV which shows allowable rivet values based on current allowable stresses given in ANC-5 and those which would result from the application of the proposed new rules. It should be emphasized that throughout this discussion only protruding-head rivets are under consideration and that the proposed rules are not intended to apply to countersunk rivets.

Figures 7, 8, 9, and 10 show the plotted data from the measurements of plate movement in the various tests. In order to establish some measure of first yielding in the specimens the same criterion previously used in bearing tests of aluminum alloys has been adopted; namely, the yield load is considered to be the load at which the permanent set per plate is equal to 2 percent of the hole diameter. Since in these specimens there were two plates of identical thickness involved in each measurement of movement, the total movement defining the yield load is twice 2 percent or 4 percent of the hole diameter, and this is the point marked on each of the curves. The resulting yield loads are listed in table I together with the corresponding shear and bearing stresses.

A study of the bearing stresses at the yield load in table I indicates that in no case was this bearing stress equal to the typical bearing yield strength of the 24S-T plates.* Since none of the bearing stresses at the yield load equals the bearing yield strength of the plates, it

*The typical bearing yield strength of the 24S-T plates is calculated to be $46,000 \times 1.6 = 73,600$ psi.

may be safely assumed that the yielding is primarily in the rivets; and, therefore, the shear stress corresponding to the yield load is probably more significant than the bearing stress. These shear stresses have been summarized in table II as shear yield strengths of the rivets. In the last column of the table the ratio of these shear yield strengths to the corresponding shear strengths is listed, and it will be noted that the minimum value of this ratio is 0.83. Since this ratio is considerably above $2/3$, it would appear that shear yield strength of rivets would never be a controlling feature in the design, and for this reason no further consideration will be given to shear yield strength in this report.

In one group of specimens involving 53S-T61 rivets a study was made of the effect of varying the thickness of the strap plate while holding the thickness of the main plate constant. The results of this study may be found listed with the rest of the values for the 53S-T61 rivets in table II. Referring to the column of ratios of shear strength to basic shear strength for 53S-T61 rivets in table II and comparing the third value with the sixth, the fourth with the seventh, and the fifth with the eighth, it becomes evident that there is practically no difference in the results whether the main plate is the same thickness as the strap plate or whether it is thicker than the strap plate. This indicates that the results of this investigation may be applied generally to single shear rivets without regard to the exact proportions of the riveted joints.

CONCLUSIONS

The following conclusions are based on tests of 1/2-inch-diameter protruding-head aluminum alloy rivets driven in aluminum alloy plates of various thicknesses:

1. The single and double shear strength of protruding head aluminum alloy rivets driven in aluminum alloy plates decreases below the "basic" value if the bearing stress exceeds about $2\frac{1}{2}$ times the shear stress on the rivet. The rate of decrease of shear strength is greater with double shear than with single shear rivets as shown in figure 3.

2. Through the use of simple straight-line formulas the shear strength of protruding-head aluminum alloy rivets driven in aluminum alloy plate can be readily predicted for various plate or sheet thicknesses as follows:

Single Shear

For values of D/t up to 3,

Single shear strength = basic allowable single shear strength

For values of D/t greater than 3,

Single shear strength = basic allowable single shear strength $\times [1 - 0.04 (D/t - 3)]$.

where

D nominal diameter of rivet, inch

t thickness of plate, inch

Double Shear

For values of D/t up to 1.5,

Double shear strength = basic allowable double shear strength

For values of D/t greater than 1.5,

Double shear strength = basic allowable double shear strength $\times [1 - 0.13 (D/t - 1.5)]$.

Aluminum Research Laboratories,
Aluminum Company of America,
New Kensington, Pa., March 31, 1944.

REFERENCE

1. Anon.: Strength of Aircraft Elements. ANQ-5, Amendment 1, Oct. 22, 1943, tables 5-14.

TABLE I.-- SINGLE SHEAR TESTS OF DRIVEN ALUMINUM ALLOY RIVETS IN 24S-T ALLOY PLATE

[All rivets 1/2 in. in diameter driven with cone-point heads in 33/64-in.-diameter holes;
shear area = 0.2088 sq in.]

Specimen	Plate thickness (in.)		Nominal D/t	Bearing area (sq in.)	Load (lb)		Shear stress (psi)		Bearing stress (psi)	
	Strap	Main			Yield*	Ultimate	Yield	Ultimate	Yield	Ultimate
53S-0 Rivets										
1	1/2	1/2	1.00	0.2578	1950	2320				
2						2265				
3						2240				
Av.					1950	2275	9,340	10,900	7,560	8,830
1	3/8	3/8	1.33	.1934	2020	2285				
2						2280				
3						2270				
Av.					2020	2280	9,670	10,910	10,430	11,780
1	1/4	1/4	2.00	.1289	1990	2295				
2						2265				
3						2270				
Av.					1990	2280	9,530	10,900	15,430	17,660
1	3/16	3/16	2.67	.0967	1990	2260				
2						2225				
3						2235				
Av.					1990	2240	9,530	10,730	20,600	23,160
1	1/8	1/8	4.00	.0645	1890	2160				
2						2135				
3						2120				
Av.					1890	2140	9,050	10,240	29,300	33,150
1	0.081	0.081	6.17	.0417	1910	2070				
2						2020				
3						2100				
Av.					1910	2065	9,150	9,880	45,800	49,480
1	.064	.064	7.81	.0330	None	1805				
2						1760				
3						1805				
Av.					None	1790	—	8,570	—	54,240

*See footnote on p. 10.

TABLE I.-- (Continued)

Specimen	Plate thickness (in.)		Nominal D/t	Bearing area (sq in.)	Load (lb)		Shear stress (psi)		Bearing stress (psi)	
	Strap	Main			Yield*	Ultimate	Yield	Ultimate	Yield	Ultimate
<u>53S-T61 Rivets</u>										
1	1/2	1/2	1.00	0.2578	None	4770	-----	23,120	-----	18,720
2						4910				
3						4800				
Av.						None	4825			
1	3/8	3/8	1.33	.1934	4750	4870	-----	23,450	-----	24,550
2						4920				
3						4900				
Av.						4750	4895	22,750	23,450	24,550
1	1/4	1/4	2.00	.1289	4650	4850	-----	23,350	-----	36,100
2						4880				
3						4895				
Av.						4650	4875	22,270	23,350	36,100
1	3/16	3/16	2.67	.0967	None	4795	-----	23,160	-----	50,000
2						4880				
3						4830				
Av.						None	4835			
1	1/8	1/8	4.00	.0645	None	4600	-----	22,110	-----	71,580
2						4640				
3						4610				
Av.						None	4615			
1	1/4	3/8	2.00	.1289	None	4870	-----	23,450	-----	37,990
2						4910				
3						4910				
Av.						None	4895			
1	3/16	3/8	2.67	.0967	None	4790	-----	23,180	-----	50,050
2						4865				
3						4865				
Av.						None	4840			

*See footnote on p. 10.

TABLE I.-- (Continued)

Specimen	Plate thickness (in.)		Nominal D/t	Bearing area (sq in.)	Load (lb)		Shear stress (psi)		Bearing stress (psi)	
	Strap	Main			Yield*	Ultimate	Yield	Ultimate	Yield	Ultimate
<u>53S-T61 Rivets</u>										
1	1/8	3/8	4.00	0.0645	4450	4620				
2						4765				
3						4620				
Av.					4450	4670	21,310	22,360	69,000	72,380
<u>53S-T Rivets</u>										
1	1/2	1/2	1.00	.2578	None	5620				
2						5520				
3						5500				
Av.					None	5545	-----	26,570	-----	21,500
1	3/8	3/8	1.33	.1934	None	5530				
2						5460				
3						5510				
Av.					None	5500	-----	26,340	-----	28,420
1	1/4	1/4	2.00	.1289	None	5470				
2						5620				
3						5500				
Av.					None	5530	-----	26,490	-----	42,900
1	3/16	3/16	2.67	.0967	None	5500				
2						5510				
3						5475				
Av.					None	5495	-----	26,320	-----	56,800
1	1/8	1/8	4.00	.0645	None	5180				
2						5270				
3						5220				
Av.					None	5225	-----	25,020	-----	81,000

*See footnote on p.10.

TABLE I.-- (Continued)

Specimen	Plate thickness (in.)		Nominal D/t	Bearing area (sq in.)	Load (lb)		Shear stress (psi)		Bearing stress (psi)	
	Strap	Main			Yield*	Ultimate	Yield	Ultimate	Yield	Ultimate
<u>17S-T Rivets</u>										
1	1/2	1/2	1.00	0.2578	6700	7340				
2						7395				
3						7390				
Av.					6700	7375	32,090	35,320	25,900	28,610
1	3/8	3/8	1.33	.1934	None	7210				
2						7290				
3						7230				
Av.					None	7245	-----	34,690	-----	37,450
1	1/4	1/4	2.00	.1289	6200	7290				
2						7260				
3						7280				
Av.					6200	7275	29,690	34,850	48,100	56,450

*Where word "none" appears, no yield was obtained because specimen failed before required permanent set (2 percent of hole diameter) was reached.

TABLE II.- SUMMARY OF DATA FROM SINGLE SHEAR TESTS

Rivet alloy	Thickness (in.)		Nominal D/t	Stress at failure (psi)		Shear yield strength (psi)	SS BSS	BS BSS	SYS BSS
	Main	Strap		Shear	Bearing				
53S-0	1/2	1/2	1.00	10,900	8,830	9,340	1.00	0.81	0.86
	3/8	3/8	1.33	10,910	11,780	9,670	1.00	1.08	.89
	1/4	1/4	2.00	10,900	17,660	9,530	1.00	1.62	.87
	3/16	3/16	2.67	10,730	23,160	9,530	.99	2.12	.87
	1/8	1/8	4.00	10,240	33,150	9,050	.94	3.04	.83
	0.081	0.081	6.17	9,880	49,480	9,150	.91	4.54	.84
	.064	.064	7.81	8,570	54,240	-----	.79	4.97	-----
53S-T61	1/2	1/2	1.00	23,120	18,720	-----	1.00	.81	-----
	3/8	3/8	1.33	23,450	25,320	22,750	1.01	1.10	.98
	1/4	1/4	2.00	23,350	37,820	22,270	1.01	1.64	.96
	3/16	3/16	2.67	23,160	50,000	-----	1.00	2.16	-----
	1/8	1/8	4.00	22,110	71,580	-----	.96	3.10	-----
	3/8	1/4	2.00	23,450	37,990	-----	1.01	1.64	-----
	3/8	3/16	2.67	23,180	50,050	-----	1.00	2.16	-----
	3/8	1/8	4.00	22,360	72,380	21,310	.97	3.13	.92
53S-T	1/2	1/2	1.00	26,570	21,500	-----	1.00	.81	-----
	3/8	3/8	1.33	26,340	28,420	-----	.99	1.07	-----
	1/4	1/4	2.00	26,490	42,900	-----	1.00	1.62	-----
	3/16	3/16	2.67	26,320	56,800	-----	.99	2.14	-----
	1/8	1/8	4.00	25,020	81,000	-----	.94	3.05	-----
17S-T	1/2	1/2	1.00	35,320	28,610	32,090	1.00	0.81	.91
	3/8	3/8	1.33	34,690	37,450	-----	.98	1.06	-----
	1/4	1/4	2.00	34,850	56,450	29,690	.99	1.60	.84

D Nominal diameter of rivet, in.
t Thickness of plate, in.
SS Shear strength of rivet, psi
BSS Basic shear strength (shear strength when D/t = 1), psi.
BS Bearing stress on rivet, psi.
All failures by shearing of rivets.

TABLE III.- SUMMARY DATA FROM DOUBLE SHEAR TESTS
 FROM PREVIOUS REPORT (42-48)
 [1/2-in. rivets in 33/64-in. holes]

Rivet alloy	Plate alloy	Nominal D/t	Stress at failure (psi)		SS BSS	BS BSS
			Shear	Bearing		
3S	17S-T	1.00	13,780	22,410	1.00	1.63
3S	17S-T	1.33	13,700	29,730	1.00	2.16
3S	17S-T	2.00	13,090	42,220	.95	3.06
3S	17S-T	2.67	11,560	49,470	.84	3.59
3S	17S-T	4.00	9,580	61,070	.70	4.44
53S-W	17S-T	1.00	21,660	35,100	1.00	1.62
53S-W	17S-T	1.33	21,150	45,820	.98	2.11
53S-W	17S-T	2.00	19,700	63,640	.91	2.94
53S-W	17S-T	2.67	17,880	76,370	.83	3.52
53S-W	17S-T	4.00	15,070	96,030	.70	4.43
53S-W	53S-T	1.00	23,470	38,560	1.00	1.64
53S-W	53S-T	1.33	23,830	51,880	1.01	2.21
53S-W	53S-T	2.00	22,500	72,750	.96	3.10

D Nominal diameter of rivet, in.
 t Thickness of plate, in.
 SS Shear strength of rivet, psi
 BSS Basic shear strength (shear strength when D/t = 1), psi
 BS Bearing stress on rivet, psi

All failures by shearing of rivets.

TABLE IV.— COMPARISON OF ALLOWABLE RIVET VALUES

BY PRESENT AND PROPOSED NEW RULES

[All values are for 3/16-in. diameter Al7S-T rivets in
0.191-in. diameter holes in 24S-T sheet using an edge
distance of 3/8 inch ($e = 2D$)]

Allowable bearing stress on sheet = 120,000* psi.

Allowable bearing stress on rivet = 100,000* psi.

Basic allowable shear stress on rivet = 30,000* psi.

Shear area = 0.0286 sq in.

D Nominal diameter of rivet, in.

Sheet thickness, t (in.)	D/t	Allowable value for one rivet (lb)			
		Single shear		Double shear	
		Present rule	Proposed new rule	Present rule	Proposed new rule
3/16	1.00	860	860	1720	1720
5/32	1.20	860	860	1720	1720
1/8	1.50	860	860	1720	1720
0.102	1.84	860	860	1720	1645
.081	2.31	860	860	1548	1540
.064	2.93	860	860	1222	1400
.051	3.68	860	836	975	1170**
.040	4.69	765	802	765	915**
.032	5.85	611	733**	611	733**

*See reference 1 (Army-Navy values).

**Controlled by bearing on sheet.

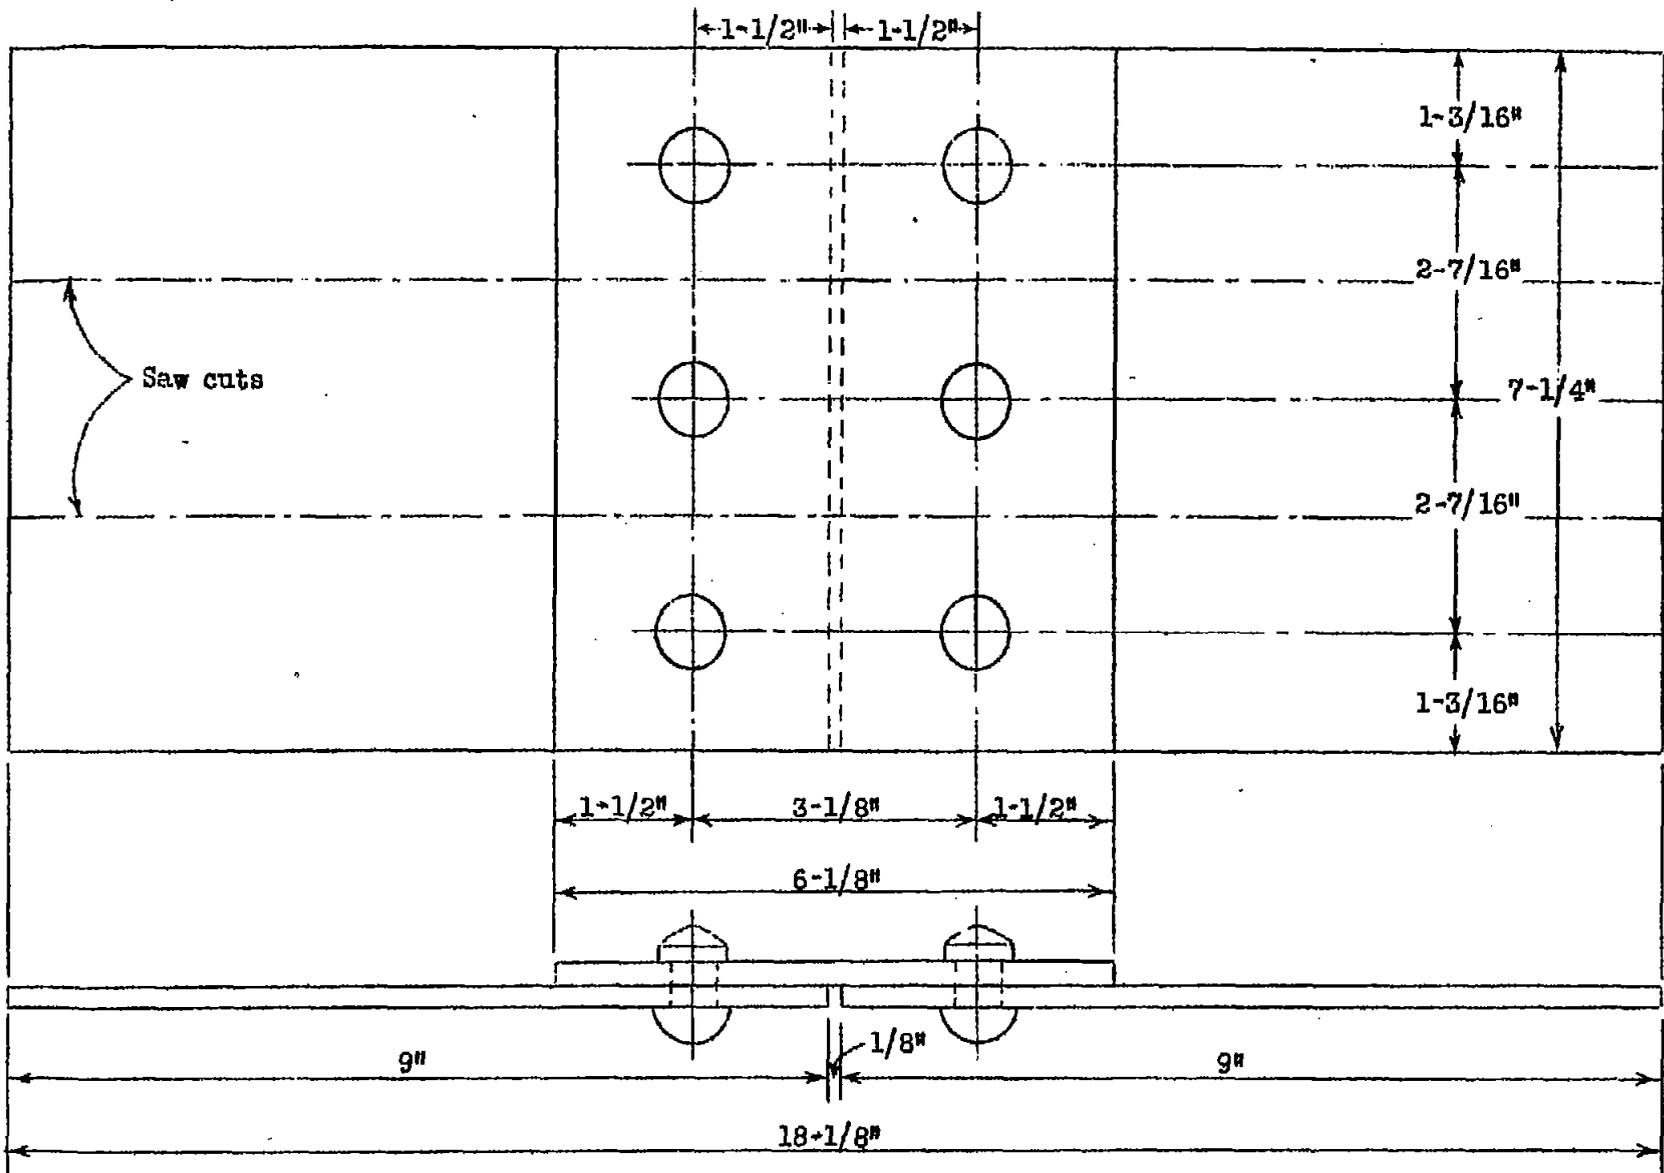


Figure 1.- Specimen for single shear tests on driven rivets (1/2" dia.) all holes 33/64" dia.



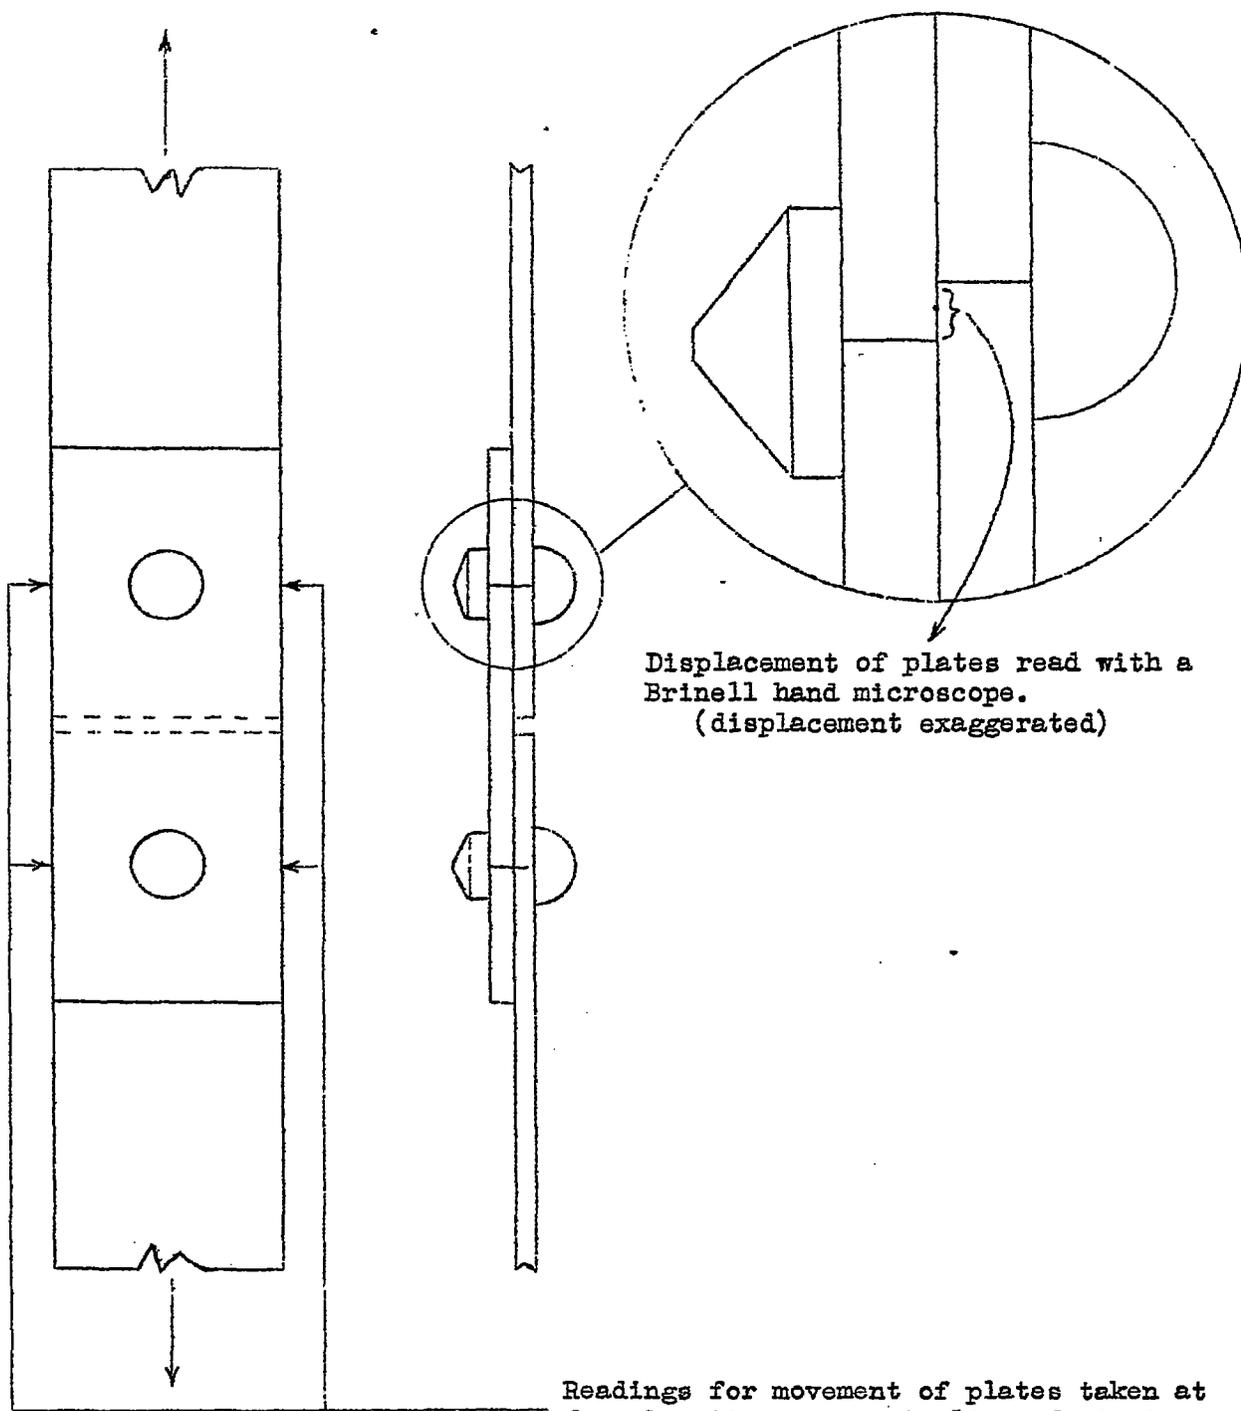


Figure 2.

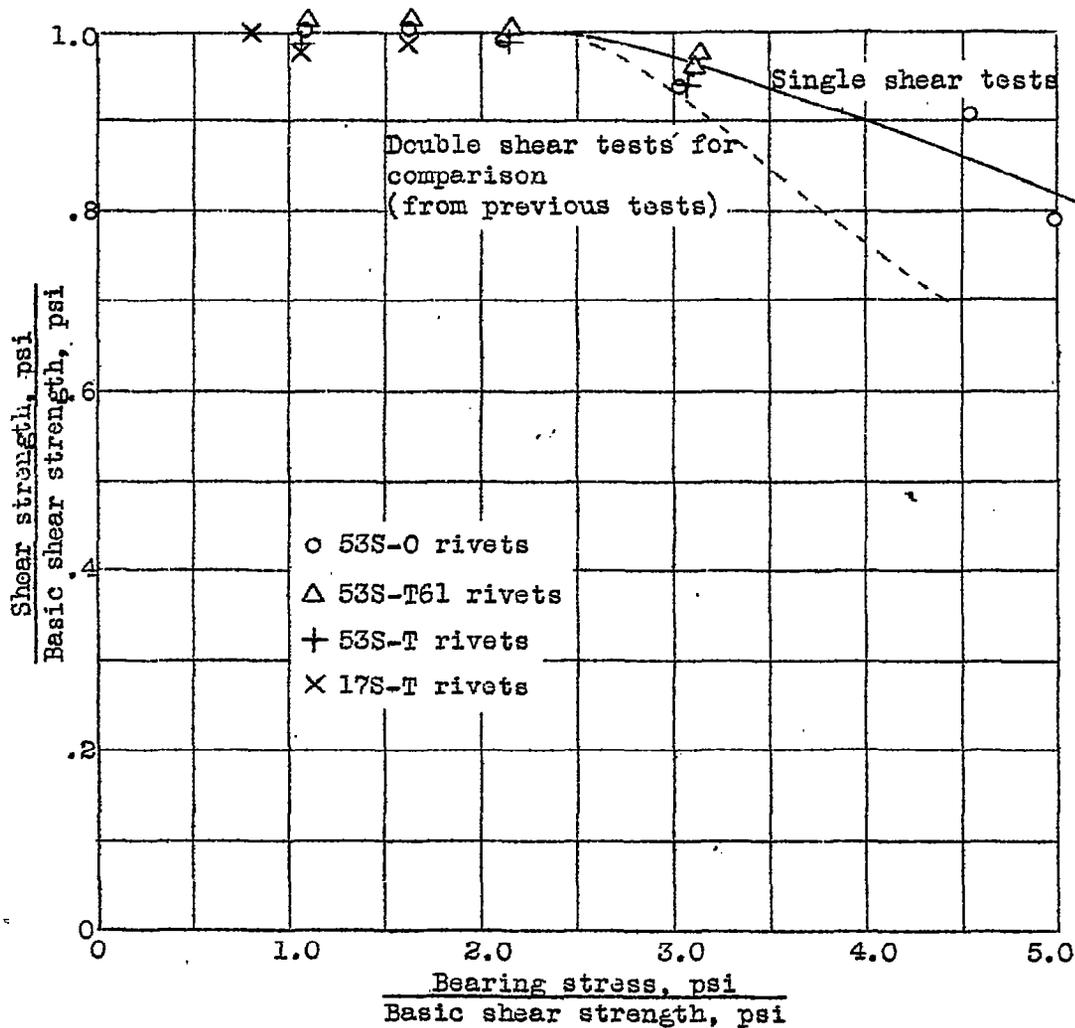


All rivets 1/2 inch in diameter driven with cone-point heads tested in single shear in 24S-T plates. Each plotted point represents average of at least three tests.

Figure 3.- Decrease in shear strength caused by increasing bearing stresses.

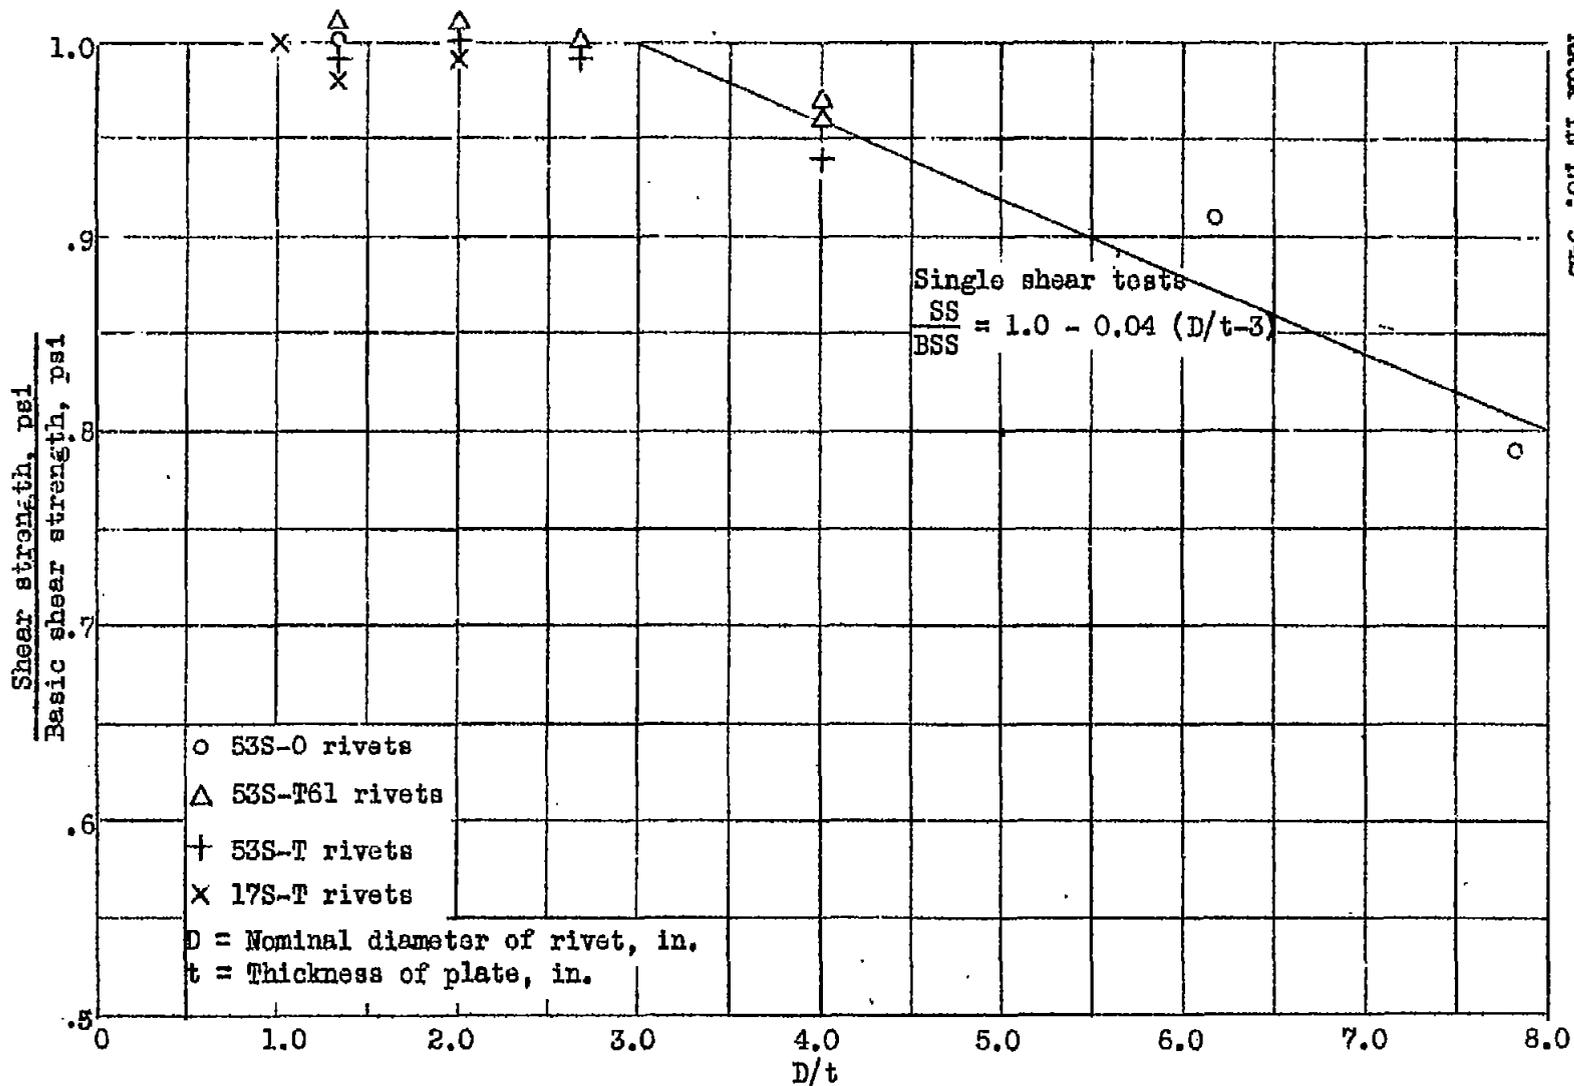

All rivets 1/2 inch in diameter, driven with cone-point heads, tested in single shear in 24S-T plates. Each plotted point represents average of at least three tests.

Figure 4.- Decrease in shear strength caused by increasing D/t ratio, single shear.

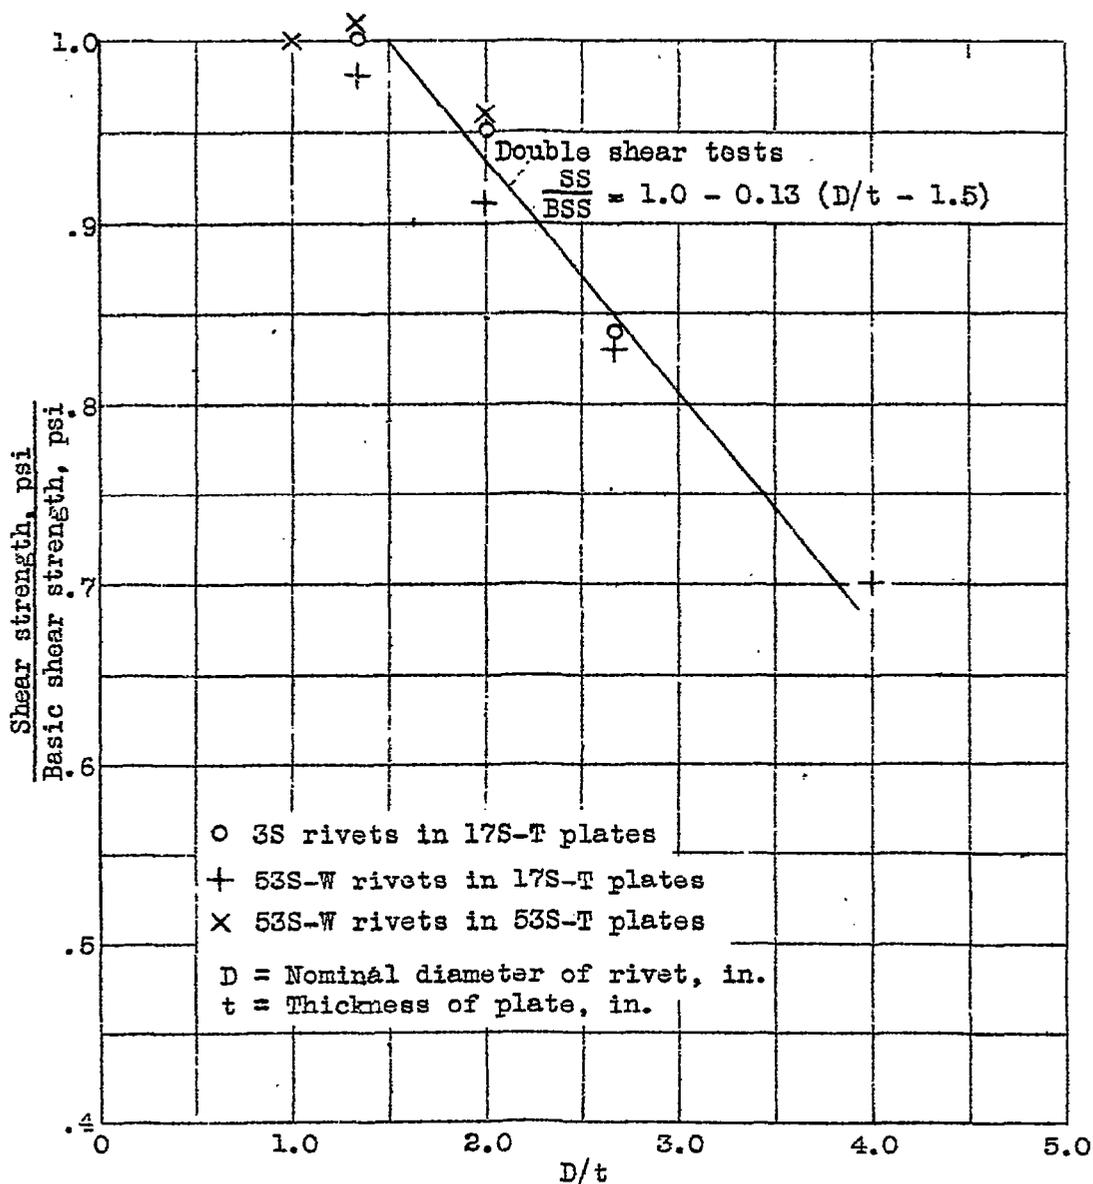

All rivets 1/2 inch in diameter driven with cone-point heads and tested in double shear. Each plotted point represents the average of at least two tests.

Figure 5.- Decrease in shear strength caused by increasing D/t ratio, double shear, :

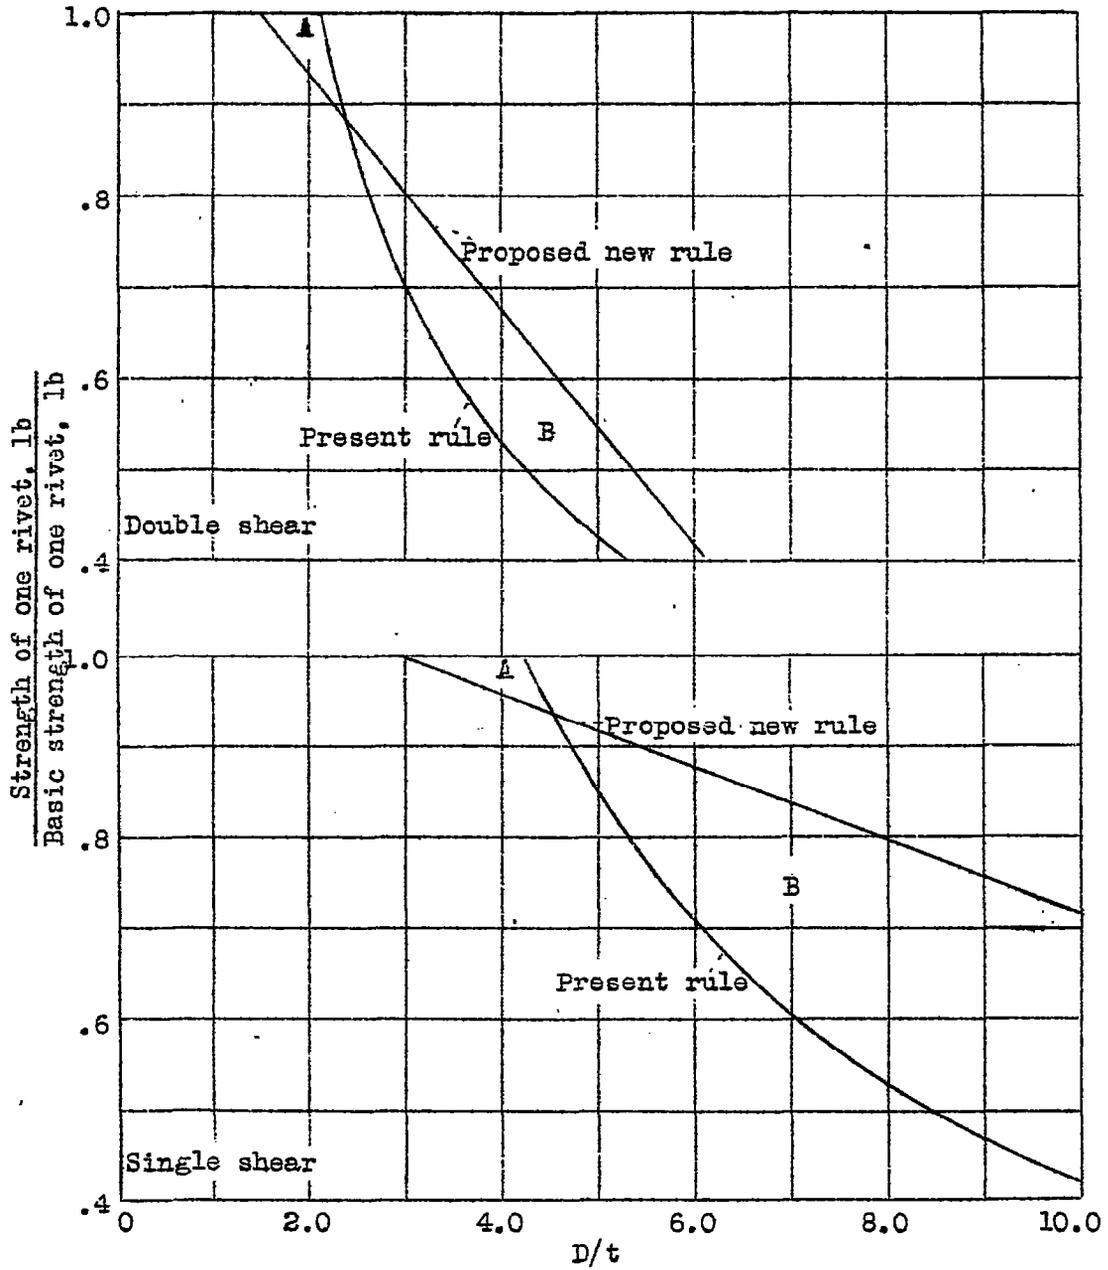


Figure 6.- Comparison of present rule and proposed new rules for effect of D/t on shear values, aluminum alloy.

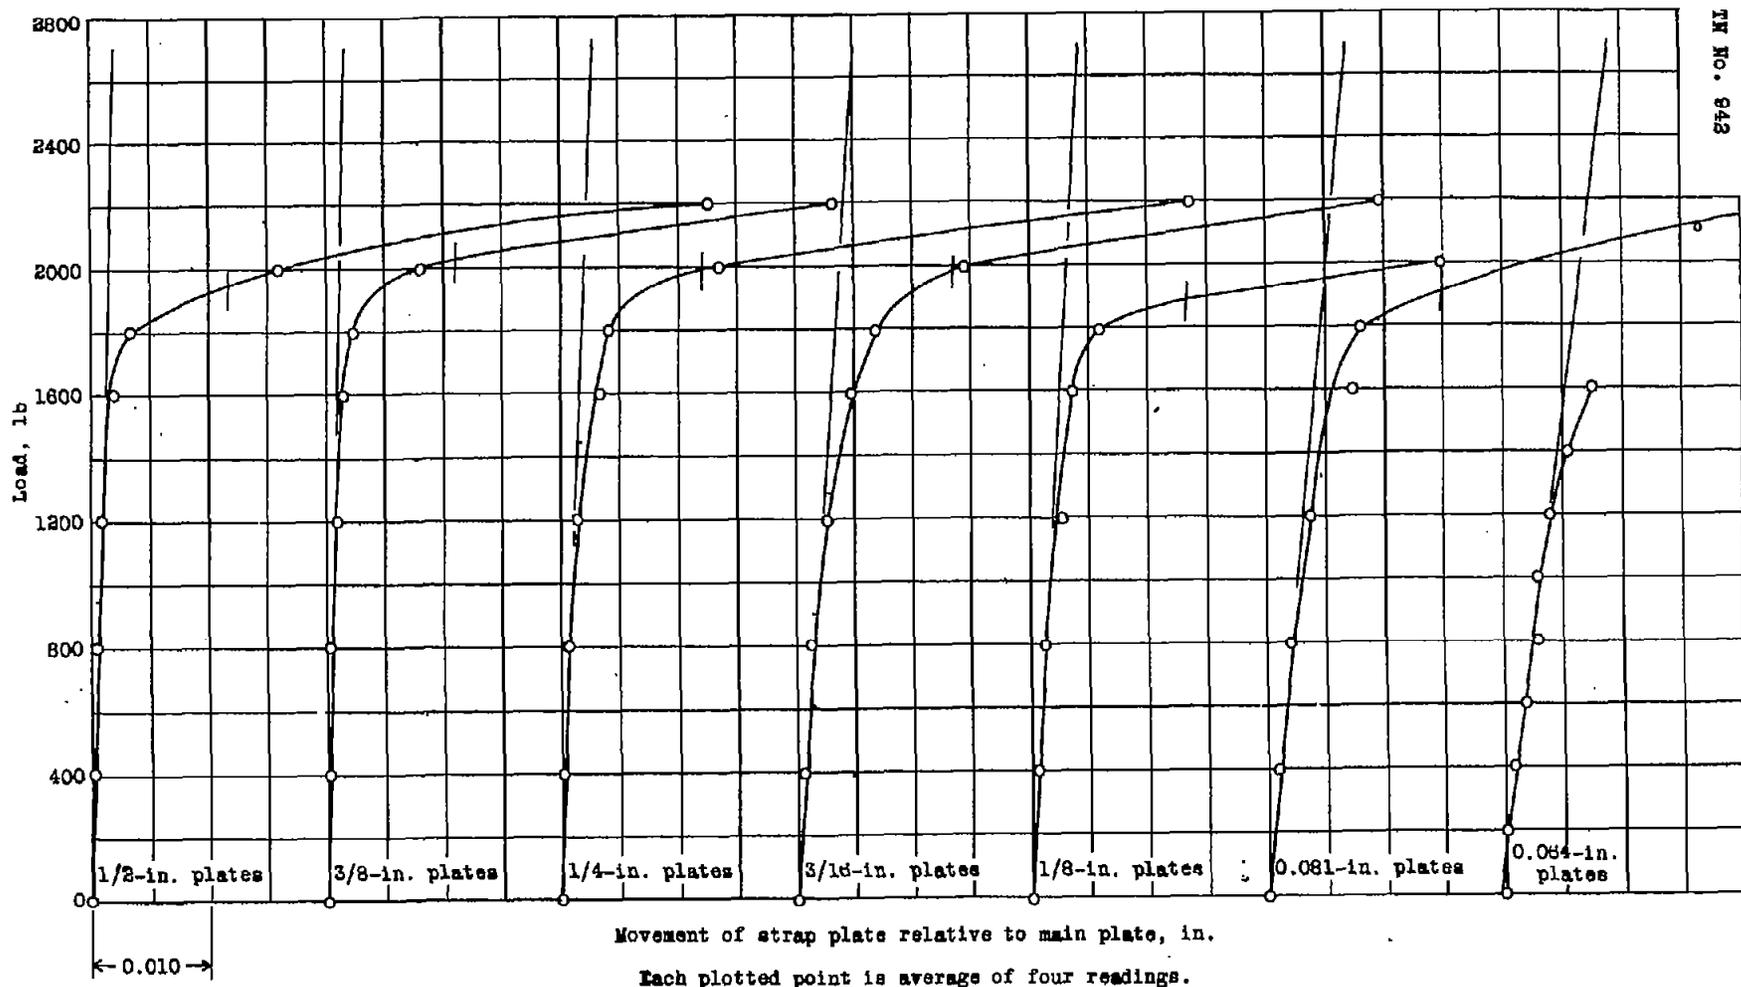


Figure 7.- Load-deformation curves for single shear riveted joints, 538-O rivets, 245-T plate.

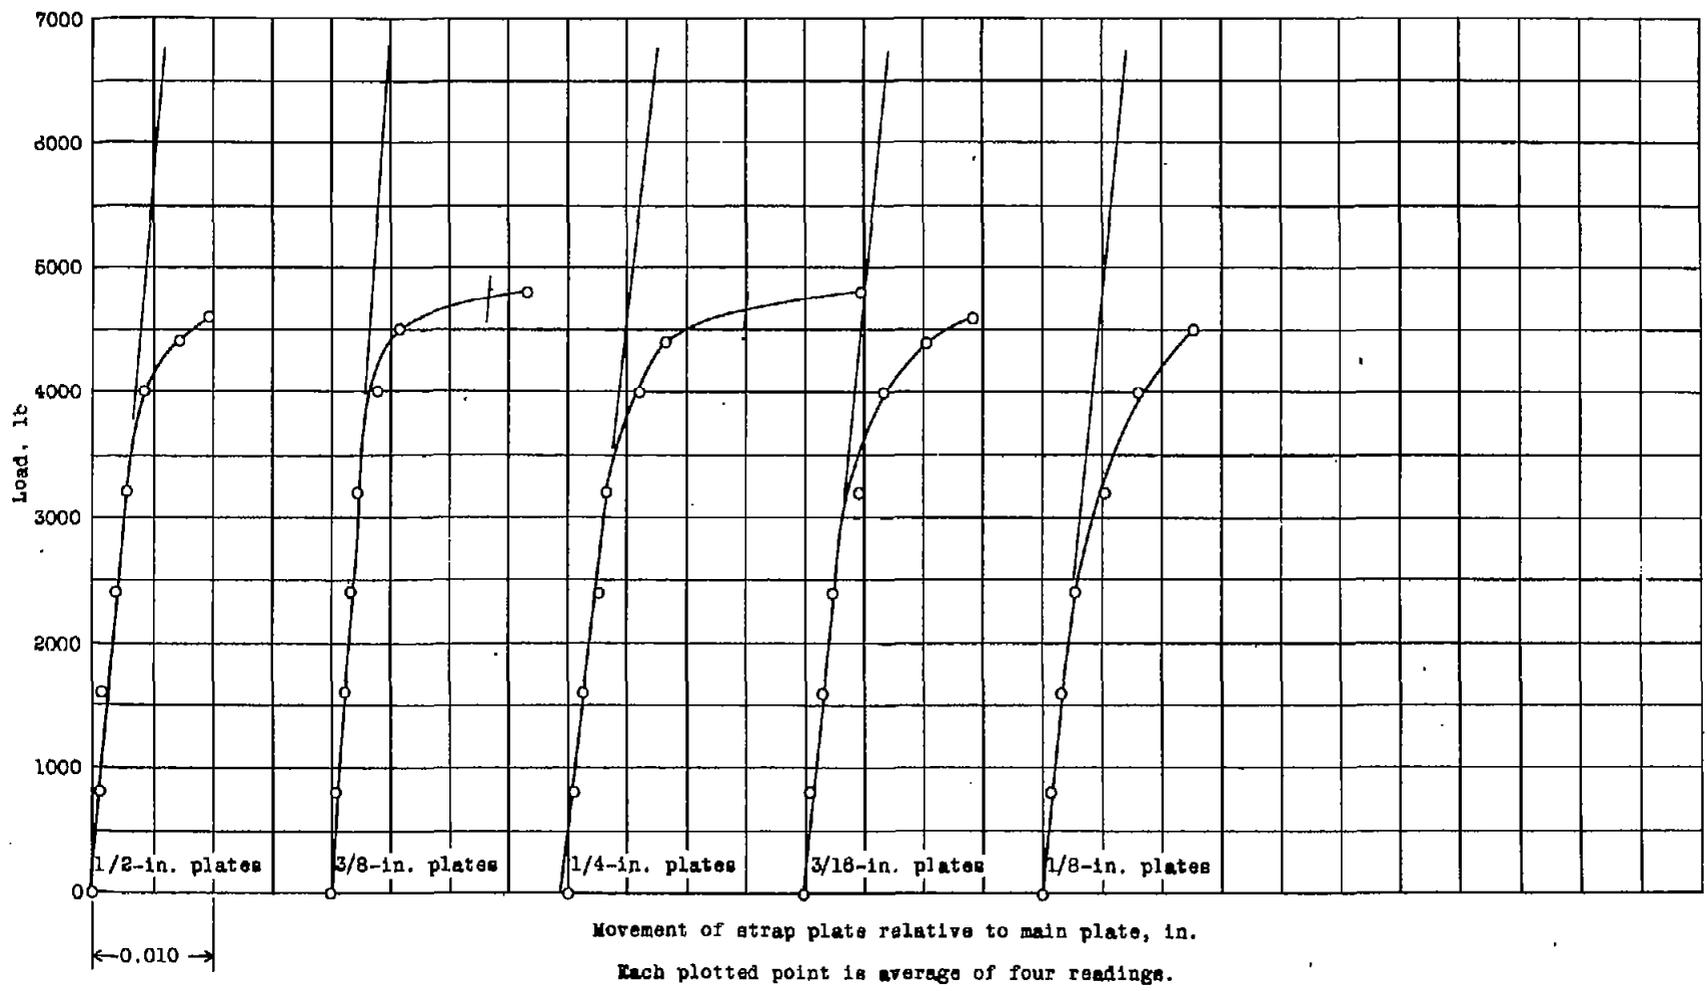


Figure 8.- Load-deformation curves for single shear riveted joints, 538-T61 rivets, 248-T plate.

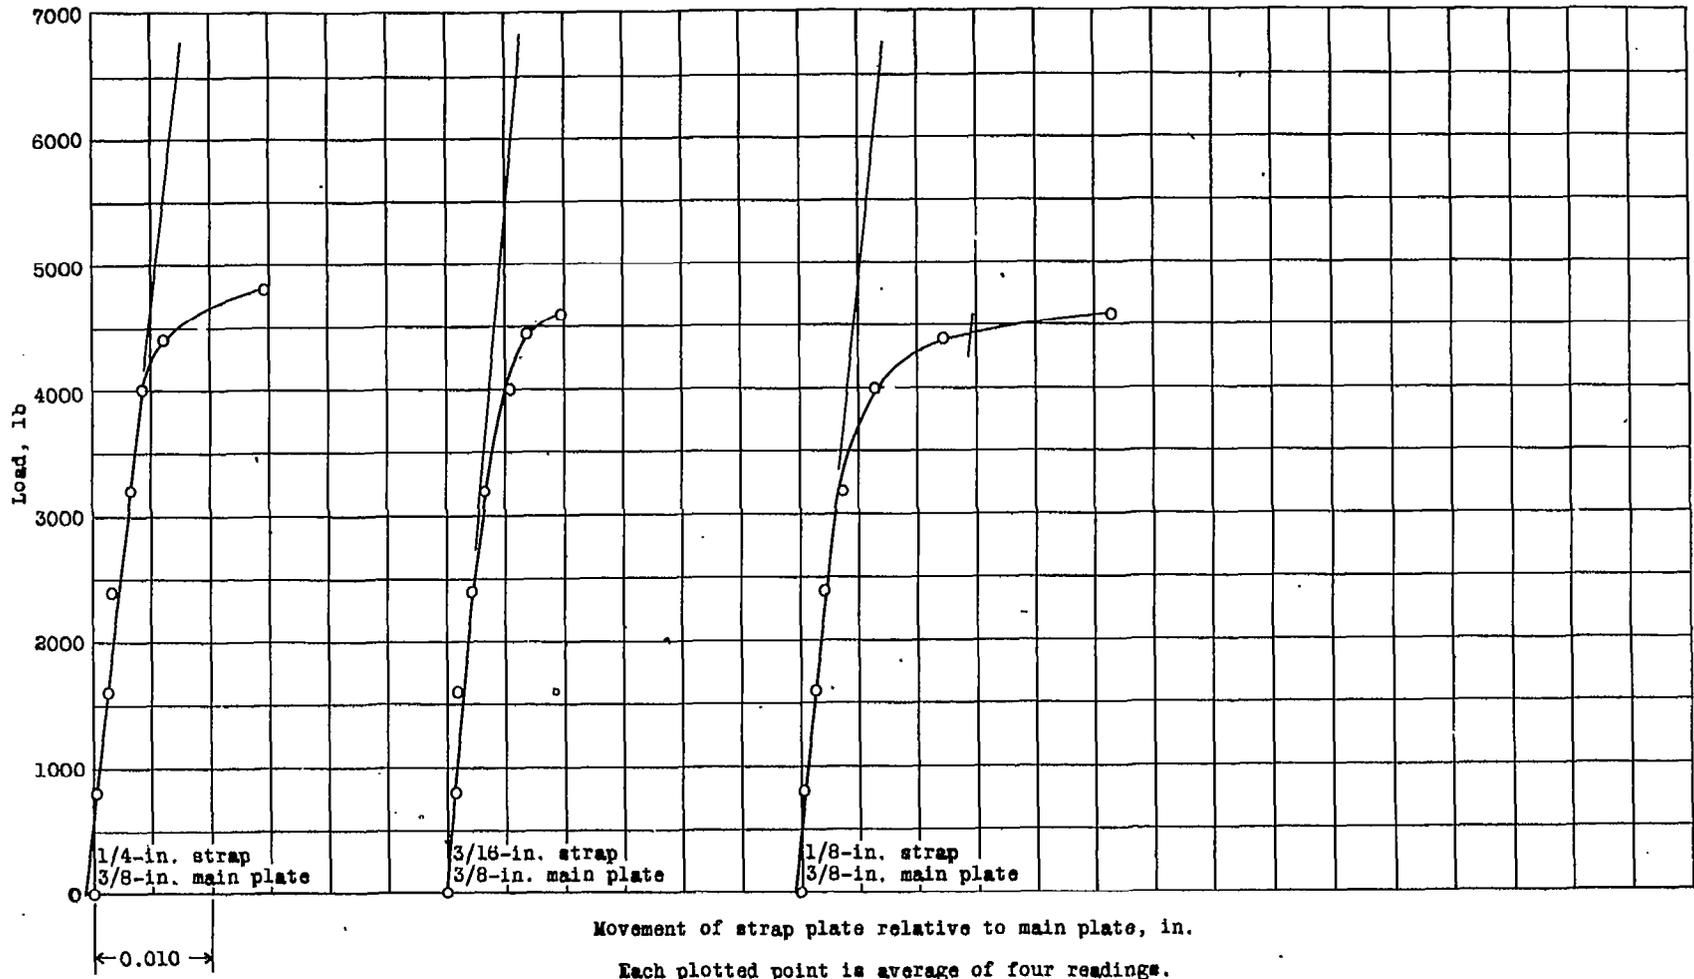


Figure 9.- Load-deformation curves for single shear riveted joints, 538-T61 rivets, 248-T plate.

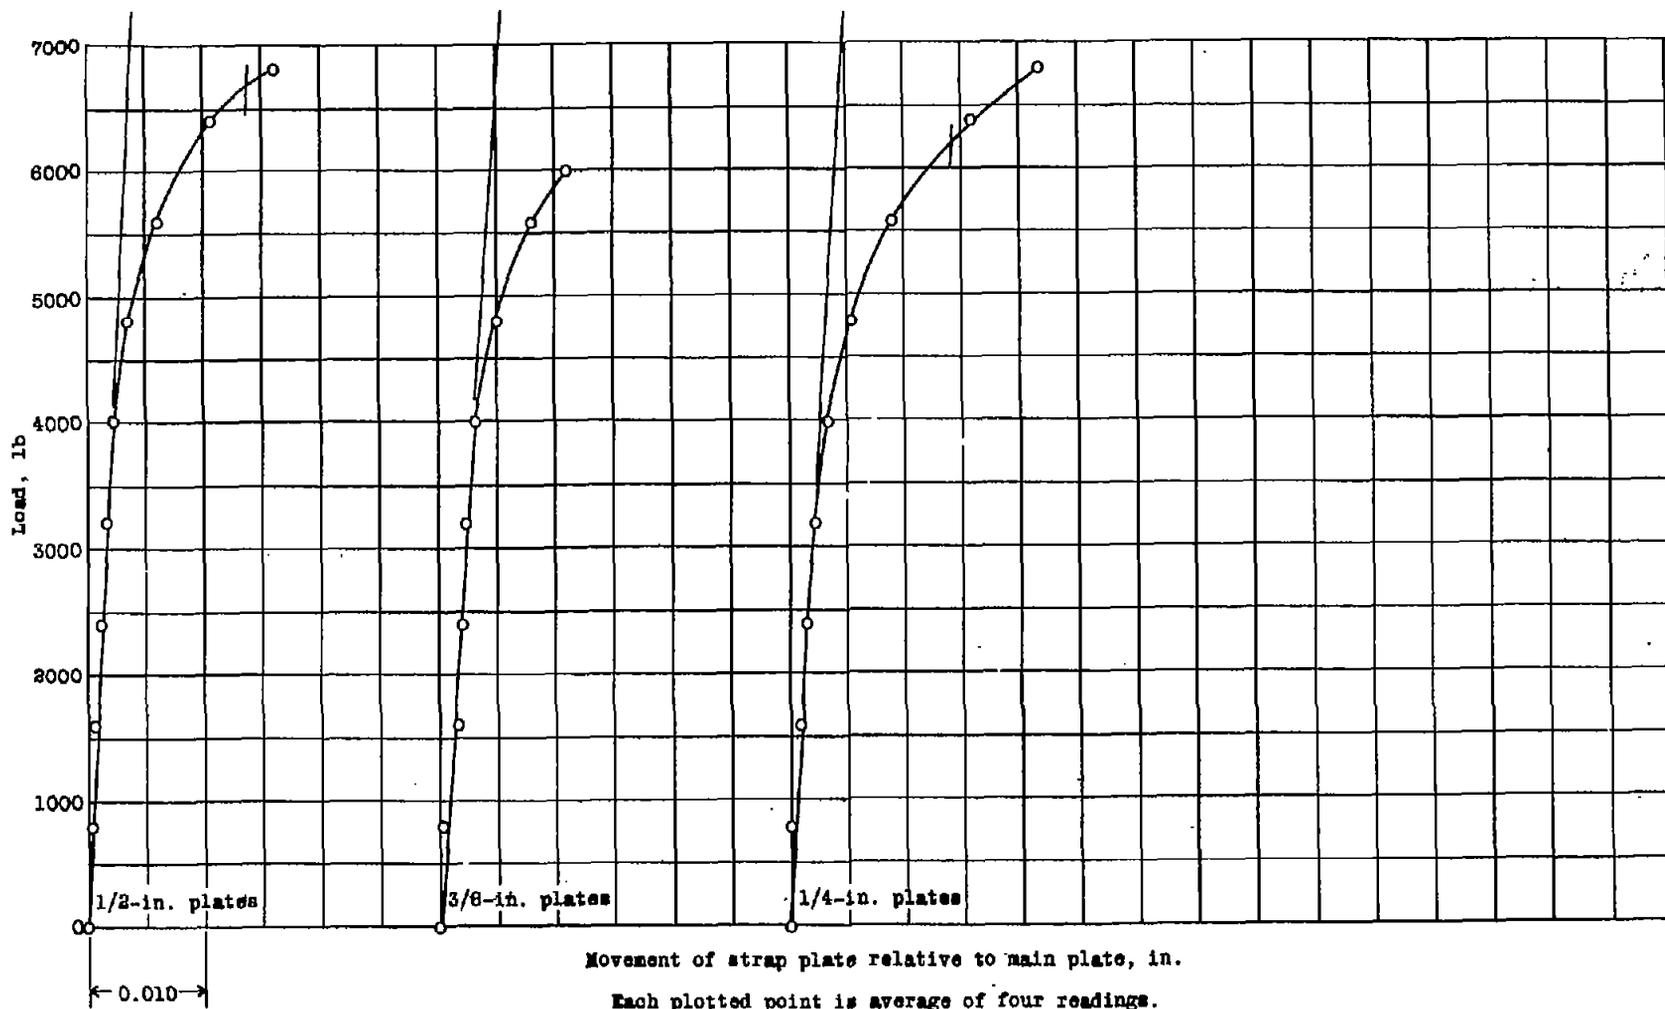


Figure 10.- Load-deformation curves for single shear riveted joints, 178-T rivets, 848-T plate.